



Role of Pullulan in preparation of ceria nanoparticles and investigation of their biological activities

Mohammad Bagher Khorrami^a, Hamid Reza Sadeghnia^b, Alireza Pasdar^{a,c},
Majid Ghayour-Mobarhan^d, Bamdad Riahi-Zanjani^e, Majid Darroudi^{f,*}

^a Department of Modern Sciences and Technologies, Faculty of Medicine, Mashhad University of Medical Sciences, Mashhad, Iran

^b Division of Neurocognitive Sciences, Psychiatry and Behavioral Sciences Research Center, Mashhad University of Medical Sciences, Mashhad, Iran

^c Division of Applied Medicine, Medical School, University of Aberdeen, Foresterhill, Aberdeen, UK

^d Biochemistry of Nutrition Research Center, Mashhad University of Medical Sciences, Mashhad, Iran

^e Medical Toxicology Research Center, Mashhad University of Medical Sciences, Mashhad, Iran

^f Nuclear Medicine Research Center, Mashhad University of Medical Sciences, Mashhad, Iran

ARTICLE INFO

Article history:

Keywords:

Ceria (CeO₂)
Nanoparticles
Pullulan
Cytotoxicity
Electron microscopy

ABSTRACT

Throughout this work, a facile, environmental–friendly, and “green” method is delineated for preparing ceria nanoparticles (CNPs), which utilizes nontoxic and renewable degraded polysaccharide polymer including pullulan as a natural matrix. Pullulan behaves as a suitable stabilizing (capping) agent for CNPs that are effectively formed at various high temperatures, while they are structurally analyzed through different techniques such as TGA/DTG, XRD, FESEM, and FTIR instruments. This procedure was found to be comparable to the ones that were acquired from conventional preparation methods that employ hazardous materials, which confirms this approach to be an exquisite alternative in preparing CNPs through the benefit of bioorganic materials. The *in vitro* cytotoxicity studies on Neuro2A cells have mentioned nontoxic particles in a range of concentrations (0.97–125 µg/ml) and thus, we reckon that the prepared particular CNPs will have persistent utilization in various fields of biology and medicine.

© 2017 Elsevier B.V. All rights reserved.

1. Introduction

The position of biopolymers and natural materials in fabricating nanoparticles, especially bioceramics, is precisely associated with the relation between green chemistry, nanoscience/nanotechnology, and nature [1–3]. Throughout recent years, synthesizing nano-bioceramics in biological matrices have been contemplated a facile, eco–friendly, safe, easily used, cost–effective, and available as a suitable alternative for the chemical and physical preparation procedures [4–6]. As significant rare–earth oxide materials, Ceria (CeO₂) nanoparticles (CNPs) have caught the interest of many in the past years since they contain unique physicochemical properties that are quite very different in comparison of those in bulk form [7]. For this reason, they have been widely reflected in various fields e.g., catalysis [8,9], fuel cells [10], specific absorbers [11], photo-protective [12], polishing [13], gas sensors [14], biomedical [15,16], and etc. A number of fabrication courses have been applied

in synthesizing CNPs, involving sol–gel [17,18], hydrothermal [19], polymeric precursor [20], co-precipitation [21,22], sonochemical [23], and microwave–assisted heating [24]. In some of the mentioned processes (e.g., an aqueous phase), surfactants and polymeric materials have been employed for the sake of improving or controlling the shape (structure) and size of CNPs. In actuality, bio-polymers including macromolecules such as polysaccharides of can be utilized as bio–substrates in the bio-synthesis of CNPs as well. When some of these particular bio-based polymers (bio-polymers) are employed as stabilizers, the size of NPs can be rationally controlled [25,26]. Fig. 1 exhibits the molecular structure of pullulan (as a neutral glucan) that contains “maltotriosyl” as a repeating unit that they are connected by α -1,6 linkages. Pullulan as an extracellular, microbial, and water-soluble polysaccharide is known as an important natural material that is can be used in different biomedical/bioengineering utilization due to unique properties e.g., non-toxic, non-mutagenic, non-immunogenic, and non-carcinogenic effects [27].

Nevertheless, there seems to be no report on the polysaccharide polymers such as pullulan as a capping and/or stabilizing agent in

* Corresponding author.

E-mail address: darroudim@mums.ac.ir (M. Darroudi).

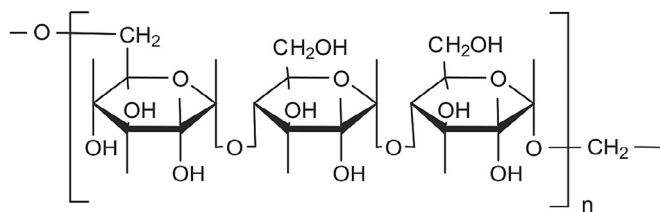


Fig. 1. Molecular structure of Pullulan.

preparing or producing CNPs. In recent years, natural-based polymers including soluble starch and gelatin, and food-based materials such as honey that stand as available, degradable, and eco-friendly templates have been utilized as bio-stabilizers in the synthesizing procedure of various materials in nanoscale [5,28–32]. Thus, pullulan was selected as a new biological template to synthesize CNPs. Thereby in this project, a modified sol-gel route was employed to synthesize of CNPs. These particular samples were first prepared using cerium nitrate hexahydrate, while pullulan was applied as a bio-template material at different temperatures.

2. Experimental

2.1. Synthesis of CNPs

To compose 4.0 g of CNPs, 10.1 g of cerium nitrate hexahydrate was dissolved in 25 ml of double distilled water and stirred for the duration of 30 min. In the meantime, 1.5 g of pullulan was dissolved in 50 ml of double distilled water and stirred for a period of 15 min at 40 °C in order to obtain a clear solution. Subsequently, the cerium precursor was added to the pullulan solution, while the flask was positioned in the bath at about 60 °C with stirring for 8 h. Then, the obtained resin was heated (3°C/min) at different respected temperatures of 400 (S₁), 500 (S₂), and 600 (S₃) for the duration of 2 h to achieve CNPs.

2.2. Characterization of CNPs

The arranged CNPs were distinguished by XRD (Philips, X'pert, Cu K_α), FTIR (ST-IR|ST-SIR spectrometer), TGA (Q600), and FESEM (Mira 3, TESCAN).

2.3. Cytotoxicity effect

Neuro2A cells were sustained in a humidified atmosphere (90%) that contained 5% CO₂ at 37 °C. Then they were cultured in Dulbecco's modified Eagle's medium (DMEM) (4.5 g/l) with fetal bovine serum (10% v/v), streptomycin (100 µg/ml), and penicillin (100 Units/ml). The cell viability was ascertained through the usage of the modified 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyl tetrazolium (MTT) assay [33]. Regarding the MTT test, about 5000 cells were seeded and processed in a range of Seo agarose concentrations (0–800 µg/ml) for a period of 24 h. The MTT in phosphate-buffered saline (PBS, 5 mg/ml) was supplemented to a final concentration of 0.05%. After 3 h, the formazan precipitate was dissolved in DMSO. The absorbance at 570 and 620 nm (background) was calculated through the utilization of a plate reader (StatFAX303). All the experiments were performed in triplicate.

3. Results and discussion

The inquiry on polymers and metal oxide NPs have caught the concern of many in last decay due to their unique properties in a large number of different applications. Furthermore, containing

oxygen-rich functionalities and the affinity towards metals and metal oxides have turned biopolymers into the best possible candidates to stabilize nanoparticles [34]. The thermogravimetric analysis (TGA/DTG) of the as-formed gel that contains pullulan and cerium derivatives are demonstrated in Fig. 2. Thermal analysis was started from about 25 °C (ambient temperature) and then was heightened up to 850 °C (10°C/min). The first weight loss observed at ~186 °C (mass loss of about 6% w/w), which would be ascribable to the volatilization of adsorbed water molecules and dehydration/condensation of formed cerium hydroxide in the gel [32]. Later on, the thermal graph of pullulan revealed a second weight loss (about 85% w/w) in some higher temperatures (240–410 °C) due to degradation of saccharide rings [35], forming and decomposing of pyrochlore phases along with the formation of crystalline CNPs and further oxidation of cerium components [36]. There is almost no weight loss that could be observed between 500 and 850 °C, indicating on the formation of thermally stabled CNPs.

Fig. 3 display the XRD patterns of obtained CNPs in diverse temperatures (400, 500, and 600 °C) that were arranged in the pullulan. The CNPs is a type of ordinary calcium fluoride crystallite structure with the space group of *Fm* $\bar{3}$ *m*. Similar crystallinity is perceived for all samples at different calcination temperatures. Bragg's peaks such as (111), (200), (220), (311), (222), (400), (331), and (420) can be confirmed the fluorite cubic crystallite structure (JCPDS #00–043–1002). The dried gel was converted into crystallite phase resulting from the heat treatment that took an increase at 400 °C (S₁). In higher calcination temperatures (500 and 600 °C), the NPs demonstrate well-defined crystallinity and the XRD patterns become sharper as the calcination temperatures heighten and peaks width decreases; this fact suggests that the crystallinity of CNPs are accelerated through the higher temperatures. The peaks width were broader for all the samples because of the combined effects of small crystal dimension and the relatively affiliated higher crystal lattice strain and defects [37,38]. Also, the broadening of XRD peaks indicate that the prepared CNPs are nanocrystalline form in nature (<20 nm) in accordance with the literature [39], while this result impresses that particles diameter of the achieved CNPs are small which is affirmed through the FESEM image of S₂ (Fig. 4).

Moreover, no diffraction features were perceived that would stand as a characteristic of byproducts e.g., Ce(OH)₄, Ce(OH)₃, and etc, denoting on the purity of CNPs. The typical mean crystallite size of the composed CNPs (S₂) was calculated from the FWHM of (111) reflection (Fig. 3b) using Scherrer formulism as rendered in Eq. (1)

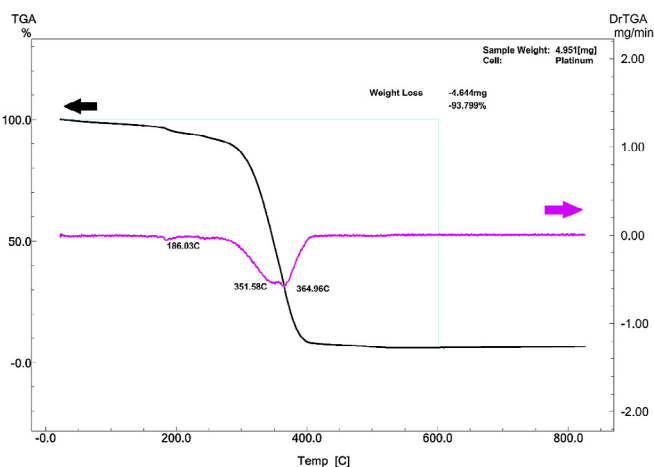


Fig. 2. TGA–DTG analysis of the Pullulan gel containing cerium cations from 25 to 850 °C.

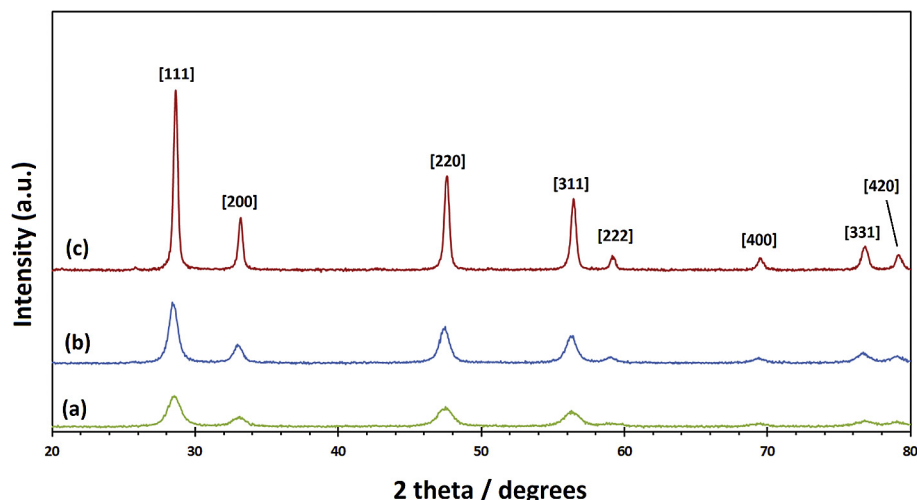


Fig. 3. XRD patterns of calcined CNPs in different temperatures; (a) 400, (b) 500, and (c) 600 °C.

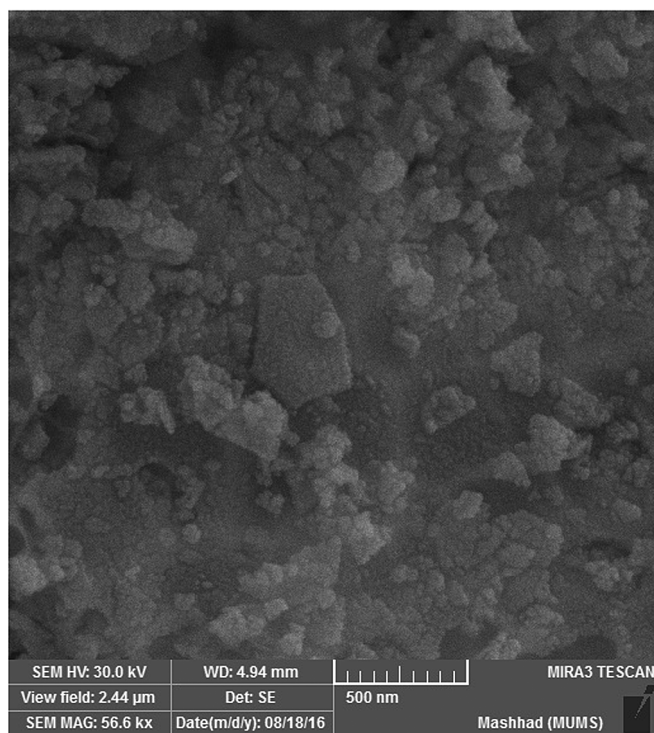


Fig. 4. FESEM image of prepared CNPs in 500 °C (S2).

[40]:

$$D = 0.9\lambda/\beta\cos\theta \quad (1)$$

where “D” stand as the crystallite size, “ λ ” would be the wavelength of the X-ray diffraction, “ β ” is the FWHM, and “ θ ” would be the angle of diffraction. It was observed that the crystallite size of the CNPs was about 12 nm. In comparison to the FESEM image, the Scherrer formulism seemed to result in lower crystallite sizes, which could be ascribed to the non-uniformity in the interplanar spacing caused by the stress in crystallites that can also lead to the broadening of XRD peaks [41]. In addition, well-defined Bragg's peaks in the XRD results affirm that the nature of CNPs was developed in a satisfying crystal quality.

Fig. 5 displays the FTIR spectra of CNPs at different calcination temperatures. The strong peaks that exist in 3444 and 1629 cm^{-1} correspond to the ν (OH) mode of (H-bonded) H_2O and δ (OH), respectively [16,42]. The FTIR spectrum of CNPs has revealed certain vibrations in 540 cm^{-1} , that is a representative phonon mode in cerium oxide (Cubic form) [43]. The band correlating to the ν (Ce–O) is noticed at 452 cm^{-1} that seems to be caused by the ν (Ce–O–Ce). A peak at 1128 cm^{-1} is probably allocated as the first overtone of the fundamental vibration [43] at about 540 cm^{-1} [44].

The cytotoxicity effect of the product (S2) on Neuro2A cells was examined thoroughly. The cell line was treated for the duration of 24 h with different CNPs concentrations (0–125 $\mu\text{g}/\text{ml}$). As it is represented in Fig. 6, no particular cytotoxic result was noticed in Neuro2A cells regarding wholly of the concentrations. This is presumed that CNPs contain the potential of improving in diverse relevant fields including optical, cosmetics, and useful devices in medical procedures. Statistical analysis was carried out by the use of ANOVA that employed SPSS software. Substantial variances were determined at $p < 0.05$.

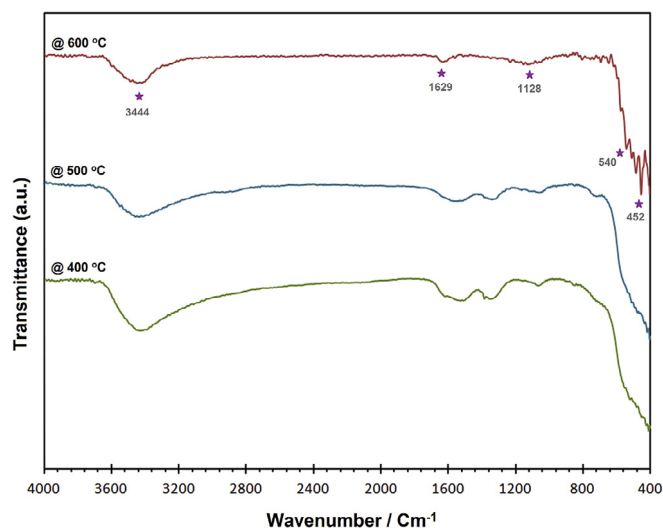


Fig. 5. FTIR spectra of calcined CNPs in various temperatures.

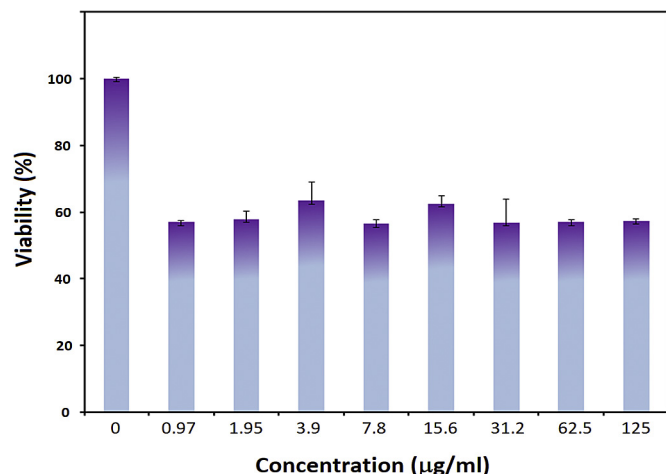


Fig. 6. Cytotoxicity result of Neuro2A cells using MTT assay (S2).

4. Conclusion

Conclusively, the production of agarose stabilized nanoceria powders have been put under examination through the sol–gel technique. Observed from the FESEM/XRD results, it was indicated that the calcined CNPs at temperatures about 500 °C disclosed homogenic NPs crystalline structure of cubic fluorite. The typical average crystallite size of CNPs was calculated through the usage of Scherrer formula, which was acquired to be about 12 nm. The *In vitro* cytotoxicity studies on Neuro2A cells revealed that all of the concentrations seemed to contain non–toxic effects.

Conflict of interest

The authors declare that they have no conflict of interest.

Acknowledgments

M. Darroudi thankfully acknowledge for technical and financial support for this project provided by Mashhad University of Medical Sciences (Grant # 930954) based on the PhD thesis of Mr. M.B. Khorrami.

References

- [1] S. Dhar, V. Mali, S. Bodhankar, A. Shiras, B. Prasad, V. Pokharkar, Biocompatible gellan gum-reduced gold nanoparticles: cellular uptake and subacute oral toxicity studies, *J. Appl. Toxicol.* 31 (5) (2011) 411–420.
- [2] M. Khatami, M.S. Nejad, S. Salari, P.G.N. Almani, Plant-mediated green synthesis of silver nanoparticles using *Trifolium resupinatum* seed exudate and their antifungal efficacy on *Neofusicocum parvum* and *Rhizoctonia solani*, *IET Nanobiotechnol.* 10 (2016) 237, 11(2) (2017) 212–212.
- [3] S. Rajeshkumar, C. Malarkodi, M. Vanaja, G. Annadurai, Anticancer and enhanced antimicrobial activity of biosynthesized silver nanoparticles against clinical pathogens, *J. Mol. Struct.* 1116 (2016) 165–173.
- [4] M. Darroudi, M. Hakimi, M. Sarani, R. Kazemi Oskuee, A. Khorsand Zak, L. Gholami, Facile synthesis, characterization, and evaluation of neurotoxicity effect of cerium oxide nanoparticles, *Ceram. Int.* 39 (6) (2013) 6917–6921.
- [5] M. Darroudi, Z. Sabouri, R. Kazemi Oskuee, A. Khorsand Zak, H. Kargar, M.H.N. Abd Hamid, Green chemistry approach for the synthesis of ZnO nanopowders and their cytotoxic effects, *Ceram. Int.* 40 (3) (2014) 4827–4831.
- [6] E. Zare, S. Pourseyedi, M. Khatami, E. Darezeshki, Simple biosynthesis of zinc oxide nanoparticles using nature's source, and its *in vitro* bio-activity, *J. Mol. Struct.* 1146 (2017) 96–103.
- [7] X. Jiao, H. Song, H. Zhao, W. Bai, L. Zhang, Y. Lv, Well-redispersed ceria nanoparticles: promising peroxidase mimetics for H₂O₂ and glucose detection, *Anal. Methods* 4 (10) (2012) 3261–3267.
- [8] Q. Fu, H. Saltsburg, M. Flytzani-Stephanopoulos, Active nonmetallic Au and Pt species on ceria-based water-gas shift catalysts, *Science* 301 (5635) (2003) 935–938.
- [9] E.D. Sherly, J.J. Vijaya, L.J. Kennedy, Effect of CeO₂ coupling on the structural, optical and photocatalytic properties of ZnO nanoparticle, *J. Mol. Struct.* 1099 (2015) 114–125.
- [10] G. Jacobs, L. Williams, U. Graham, D. Sparks, B.H. Davis, Low-temperature water-gas shift: in-situ DRIFTS– reaction study of a Pt/CeO₂ catalyst for fuel cell reformer applications, *J. Phys. Chem. B* 107 (38) (2003) 10398–10404.
- [11] R. Li, S. Yabe, M. Yamashita, S. Momose, S. Yoshida, S. Yin, T. Sato, Synthesis and UV-shielding properties of ZnO-and CaO-doped CeO₂ via soft solution chemical process, *Solid State Ionics* 151 (1) (2002) 235–241.
- [12] M.A. Marzouk, H.A. Elbatal, A.M. Abdel Ghany, F.M. Ezz Eldin, Ultraviolet, visible, ESR, and infrared spectroscopic studies of CeO₂-doped lithium phosphate glasses and effect of gamma irradiation, *J. Mol. Struct.* 997 (1–3) (2011) 94–102.
- [13] D.G. Shchukin, R.A. Caruso, Template synthesis and photocatalytic properties of porous metal oxide spheres formed by nanoparticle infiltration, *Chem. Mater.* 16 (11) (2004) 2287–2292.
- [14] P. Jasinski, T. Suzuki, H.U. Anderson, Nanocrystalline undoped ceria oxygen sensor, *Sensors Actuat. B Chem.* 95 (1) (2003) 73–77.
- [15] C.W. Younce, K. Wang, P.E. Kolattukudy, Hyperglycaemia-induced cardiomyocyte death is mediated via MCP-1 production and induction of a novel zinc-finger protein MCPIP, *Cardiovasc. Res.* 87 (4) (2010) 665–674.
- [16] H. Kargar, F. Ghasemi, M. Darroudi, Bioorganic polymer-based synthesis of cerium oxide nanoparticles and their cell viability assays, *Ceram. Int.* 41 (1, Part B) (2015) 1589–1594.
- [17] H. Kargar, H. Ghazavi, M. Darroudi, Size-controlled and bio-directed synthesis of ceria nanopowders and their *in vitro* cytotoxicity effects, *Ceram. Int.* 41 (3, Part A) (2015) 4123–4128.
- [18] A. Akbari, M. Khammar, D. Taherzadeh, A. Rajabian, A. Khorsand Zak, M. Darroudi, Zinc-doped cerium oxide nanoparticles: sol-gel synthesis, characterization, and investigation of their *in vitro* cytotoxicity effects, *J. Mol. Struct.* 1149 (2017) 771–776.
- [19] A.I.Y. Tok, F.Y.C. Boey, Z. Dong, X. Sun, Hydrothermal synthesis of CeO₂ nanoparticles, *J. Mater. Process. Technol.* 190 (1) (2007) 217–222.
- [20] R. Rocha, E. Muccillo, Preparation and Characterization of Ce_{0.8}Gd_{0.2}O_{1.9} solid Electrolyte by Polymeric Precursor Techniques, *Mater. Sci. Forum Trans. Tech. Publ.* (2003) 711–719.
- [21] M. Darroudi, M. Sarani, R. Kazemi Oskuee, A. Khorsand Zak, M.S. Amiri, Nanoceria: gum mediated synthesis and *in vitro* viability assay, *Ceram. Int.* 40 (2) (2014) 2863–2868.
- [22] M. Darroudi, M. Sarani, R. Kazemi Oskuee, A. Khorsand Zak, H.A. Hosseini, L. Gholami, Green synthesis and evaluation of metabolic activity of starch mediated nanoceria, *Ceram. Int.* 40 (1, Part B) (2014) 2041–2045.
- [23] C.Y. Jimmy, L. Zhang, J. Lin, Direct sonochemical preparation of high-surface-area nanoporous ceria and ceria–zirconia solid solutions, *J. Colloid Interface Sci.* 260 (1) (2003) 240–243.
- [24] M.M. Natile, G. Boccaletti, A. Glisenti, Properties and reactivity of nano-structured CeO₂ powders: comparison among two synthesis procedures, *Chem. Mater.* 17 (25) (2005) 6272–6286.
- [25] M. Darroudi, M.B. Ahmad, A.H. Abdullah, N.A. Ibrahim, Green synthesis and characterization of gelatin-based and sugar-reduced silver nanoparticles, *Int. J. Nanomed.* 6 (2011) 569.
- [26] M. Darroudi, M. Bagherpour, H.A. Hosseini, M. Ebrahimi, Biopolymer-assisted green synthesis and characterization of calcium hydroxide nanoparticles, *Ceram. Int.* 42 (3) (2016) 3816–3819.
- [27] M. Rekha, C.P. Sharma, Pullulan as a promising biomaterial for biomedical applications: a perspective, *Trends Biomater. Artif. Organs* 20 (2) (2007) 116–121.
- [28] M. Darroudi, M.B. Ahmad, M. Hakimi, R. Zamiri, A.K. Zak, H.A. Hosseini, M. Zargar, Preparation, characterization, and antibacterial activity of γ -irradiated silver nanoparticles in aqueous gelatin, *Int. J. Miner. Metall. Mater.* 20 (4) (2013) 403–409.
- [29] M. Darroudi, M.B. Ahmad, M. Mashreghi, Gelatinous silver colloid nanoparticles: synthesis, characterization, and their antibacterial activity, *J. Optoelectron. Adv. Mater.* 16 (1–2) (2014) 182–187.
- [30] M. Darroudi, M.B. Ahmad, A.K. Zak, R. Zamiri, M. Hakimi, Fabrication and characterization of gelatin stabilized silver nanoparticles under UV-Light, *Int. J. Mol. Sci.* 12 (9) (2011) 6346–6356.
- [31] M. Darroudi, M. Hakimi, E. Goodarzi, R. Kazemi Oskuee, Superparamagnetic iron oxide nanoparticles (SPIONs): green preparation, characterization and their cytotoxicity effects, *Ceram. Int.* 40 (9, Part B) (2014) 14641–14645.
- [32] M. Darroudi, S.J. Hoseini, R. Kazemi Oskuee, H.A. Hosseini, L. Gholami, S. Gerayli, Food-directed synthesis of cerium oxide nanoparticles and their neurotoxicity effects, *Ceram. Int.* 40 (5) (2014) 7425–7430.
- [33] T. Mosmann, Rapid colorimetric assay for cellular growth and survival: application to proliferation and cytotoxicity assays, *J. Immunol. Methods* 65 (1–2) (1983) 55–63.
- [34] J. Liu, F. He, E. Durham, D. Zhao, C.B. Roberts, Polysugar-stabilized Pd nanoparticles exhibiting high catalytic activities for hydrodechlorination of environmentally deleterious trichloroethylene, *Langmuir* 24 (1) (2008) 328–336.
- [35] E. Trovatti, S.C.M. Fernandes, L. Rubatat, C.S.R. Freire, A.J.D. Silvestre, C.P. Neto, Sustainable nanocomposite films based on bacterial cellulose and pullulan, *Cellulose* 19 (3) (2012) 729–737.
- [36] L. Li, Y. Chen, Preparation of nanometer-scale CeO₂ particles via a complex thermo-decomposition method, *Mater. Science Eng. A* 406 (1) (2005)

- 180–185.
- [37] S. Deshpande, S. Patil, S.V. Kuchibhatla, S. Seal, Size dependency variation in lattice parameter and valency states in nanocrystalline cerium oxide, *Appl. Phys. Lett.* 87 (13) (2005), 133113.
- [38] M. Darroudi, M. Sarani, R. Kazemi Oskuee, A. Khorsand Zak, H.A. Hosseini, L. Gholami, Green synthesis and evaluation of metabolic activity of starch mediated nanoceria, *Ceram. Int.* 40 (1 PART B) (2014) 2041–2045.
- [39] A. Khorsand Zak, W.H. Abd Majid, M.R. Mahmoudian, M. Darroudi, R. Yousefi, Starch-stabilized synthesis of ZnO nanopowders at low temperature and optical properties study, *Adv. Powder Technol.* 24 (3) (2013) 618–624.
- [40] F. Bondioli, A. Bonamartini Corradi, C. Leonelli, T. Manfredini, Nanosized CeO₂ powders obtained by flux method, *Mater. Res. Bull.* 34 (14) (1999) 2159–2166.
- [41] E. Ahmed, M.S. Abid, W. Ahmed, Growth of nano size grains in CuInSe₂ thin films using E-beam deposition technique, *J. Nanosci. Nanotechnol.* 9 (7) (2009) 4233–4239.
- [42] H. Wang, J.-J. Zhu, J.-M. Zhu, X.-H. Liao, S. Xu, T. Ding, H.-Y. Chen, Preparation of nanocrystalline ceria particles by sonochemical and microwave assisted heating methods, *Phys. Chem. Chem. Phys.* 4 (15) (2002) 3794–3799.
- [43] A.Q. Wang, N. D'Souza, T.D. Golden, Electrosynthesis of nanocrystalline cerium oxide/layered silicate powders, *J. Mater. Chem.* 16 (5) (2006) 481–488.
- [44] B. Yan, H. Zhu, Controlled synthesis of CeO₂ nanoparticles using novel amphiphilic cerium complex precursors, *J. Nanoparticle Res.* 10 (8) (2008) 1279–1285.